

12-11-2004

Sm₂NalrO₆, A Monoclinically Distorted Double Perovskite

Samuel J. Mugavero III
University of South Carolina - Columbia

Irina V. Puzdrjakova
University of South Carolina - Columbia

Mark D. Smith
University of South Carolina - Columbia, mdsmith3@mailbox.sc.edu

Hans-Conrad zur Loye
University of South Carolina - Columbia, zurloye@mailbox.sc.edu

Follow this and additional works at: https://scholarcommons.sc.edu/chem_facpub

 Part of the [Chemistry Commons](#)

Publication Info

Published in *Acta Crystallographica Section E*, Volume 61, Issue 1, 2004, pages i3-i5.

This Article is brought to you by the Chemistry and Biochemistry, Department of at Scholar Commons. It has been accepted for inclusion in Faculty Publications by an authorized administrator of Scholar Commons. For more information, please contact digres@mailbox.sc.edu.

Acta Crystallographica Section E

Structure Reports

Online

ISSN 1600-5368

Editors: **W. Clegg** and **D. G. Watson**

Sm₂NalrO₆, a monoclinically distorted double perovskite

Samuel J. Mugavero III, Irina V. Puzdrjakova, Mark D. Smith and Hans-Conrad zur Loye

Copyright © International Union of Crystallography

Author(s) of this paper may load this reprint on their own web site provided that this cover page is retained. Republication of this article or its storage in electronic databases or the like is not permitted without prior permission in writing from the IUCr.

Sm₂NaIrO₆, a monoclinically distorted double perovskite

Samuel J. Mugavero III, Irina V. Puzdrjakova, Mark D. Smith and Hans-Conrad zur Loye*

Department of Chemistry and Biochemistry,
University of South Carolina, Columbia,
South Carolina 29208, USA

Correspondence e-mail: zurloye@sc.edu

Key indicators

Single-crystal X-ray study
 $T = 294\text{ K}$
Mean $\sigma(\text{m-O}) = 0.004\text{ \AA}$
 R factor = 0.026
 wR factor = 0.052
Data-to-parameter ratio = 22.2

For details of how these key indicators were automatically derived from the article, see <http://journals.iucr.org/e>.

Single crystals of the lanthanide-containing iridate, disamarium sodium iridium hexaoxide, Sm₂NaIrO₆, were prepared *via* high-temperature flux growth and structurally characterized by single-crystal X-ray diffraction. The compound crystallizes in the monoclinic space group $P2_1/n$ and is a double perovskite, consisting of a 1:1 ordered rock-salt-type lattice of corner-shared NaO₆ and IrO₆ distorted octahedra. Samarium occupies the eightfold coordination site generated by the connectivity of the octahedra.

Received 22 November 2004

Accepted 1 December 2004

Online 11 December 2004

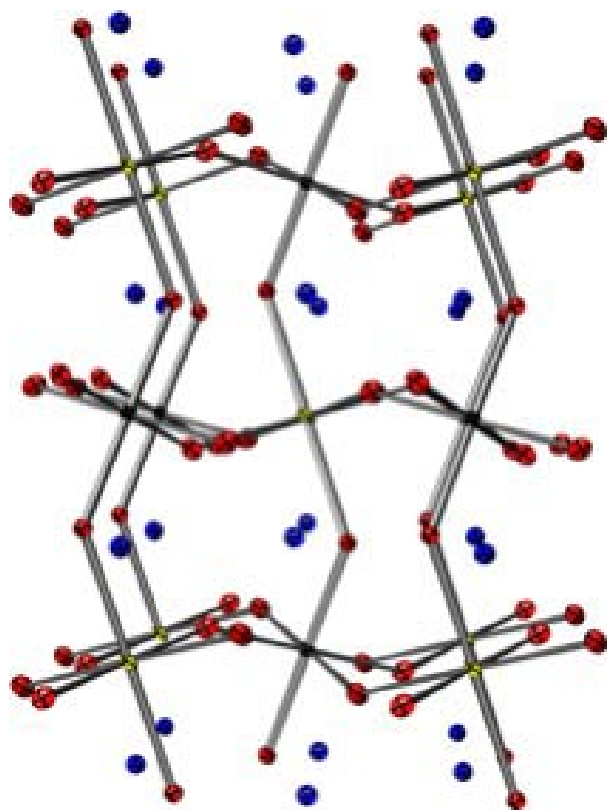
Comment

Recently the crystal growth and characterization of the double perovskites Ln₂LiIrO₆ (Ln = La, Pr, Nd, Sm and Eu) and Ln₂NaMO₆ (Ln = La, Pr and Nd, and $M = \text{Ru}$ and Ir) from molten hydroxide fluxes was reported (Gemmill *et al.*, 2004; Davis *et al.*, 2004; Mugavero *et al.*, 2005). High-temperature flux growth from molten hydroxides has proven to be an effective medium for oxide crystal growth. Sm₂NaIrO₆, a distorted double perovskite, was grown from a molten NaOH/CsOH flux at 923 K.

In its ideal form, the cubic perovskite ABO₃ consists of corner-sharing BO₆ octahedra with the A cation occupying the 12-fold coordination site formed in the middle of a cube of eight such octahedra (Mitchell, 2002). The ideal double perovskite structure of the general formula A₂BB'O₆ is obtained when the B cation is substituted by a B' cation in an ordered 1:1 fashion, doubling the unit cell. The $P2_1/n$ space group allows for a 1:1 ordered arrangement of the B and B' cations in a rock-salt-type lattice and the tilting of the BO₆ and B'O₆ octahedra to accommodate the small size of the A cation (Woodward, 1997*a,b*). The Glazer tilt system assigned to the $P2_1/n$ space group is #10, $a^-a^-b^+$ (Glazer, 1972). Sm₂NaIrO₆ is a monoclinically distorted structure of an ideal double perovskite where the Na⁺ and Ir⁵⁺ cations occupy the two crystallographically independent octahedral sites (site symmetry $\bar{1}$, Wyckoff symbol 2*a*; site symmetry $\bar{1}$, Wyckoff symbol 2*b*), while the Sm³⁺ cations occupy the A site in an eightfold coordination environment (site symmetry 1, Wyckoff symbol 4*e*).

Experimental

Single crystals of Sm₂NaIrO₆ were grown from an 'acidic' high-temperature hydroxide melt. Sm₂O₃ (Alfa Aesar 99.9%, 0.75 mmol), Ir (Engelhard, 99.9%, 0.5 mmol), NaOH (Fisher, ACS reagent, 3.0 g) and CsOH (Alfa Aesar, 98%, 2.0 g) were loaded into a silver tube that had been previously flame-sealed at one end. The top of the tube was crimped and folded three times before being placed upright into a programmable box furnace. The tube was heated to 923 K over a

**Figure 1**

Octahedral tilting in $\text{Sm}_2\text{NaIrO}_6$, with the [010] direction shown going into the page and displacement ellipsoids drawn at the 50% probability level. Sm^{3+} shown in blue, Ir^{5+} in black, Na^+ in yellow and O^{2-} in red.

period of 1 h, held at that temperature for 24 h and then cooled to room temperature by shutting off the furnace. The black dodecahedral-shaped crystals were removed from the flux matrix by dissolving the flux in water and isolating the crystals by vacuum filtration.

Crystal data

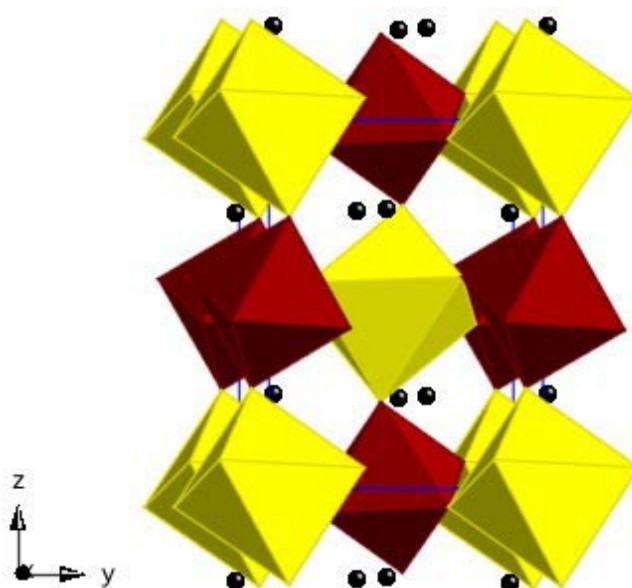
$\text{Sm}_2\text{NaIrO}_6$	$D_x = 8.024 \text{ Mg m}^{-3}$
$M_r = 611.89$	Mo $K\alpha$ radiation
Monoclinic, $P2_1/n$	Cell parameters from 3184 reflections
$a = 5.4656(2) \text{ \AA}$	$\theta = 2.6\text{--}35.0^\circ$
$b = 5.8880(2) \text{ \AA}$	$\mu = 49.13 \text{ mm}^{-1}$
$c = 7.8714(3) \text{ \AA}$	$T = 294(1) \text{ K}$
$\beta = 91.097(1)^\circ$	Prism, black
$V = 253.27(2) \text{ \AA}^3$	$0.06 \times 0.04 \times 0.04 \text{ mm}$
$Z = 2$	

Data collection

Bruker SMART APEX CCD diffractometer	1112 independent reflections
ω scans	1049 reflections with $I > 2\sigma(I)$
Absorption correction: multi-scan, (SADABS; Bruker, 2001)	$R_{\text{int}} = 0.032$
$T_{\text{min}} = 0.075$, $T_{\text{max}} = 0.140$	$\theta_{\text{max}} = 35.1^\circ$
4588 measured reflections	$h = -8 \rightarrow 8$
	$k = -9 \rightarrow 8$
	$l = -12 \rightarrow 12$

Refinement

Refinement on F^2	$w = 1/[\sigma^2(F_o^2) + (0.0142P)^2 + 3.1589P]$
$R[F^2 > 2\sigma(F^2)] = 0.026$	where $P = (F_o^2 + 2F_c^2)/3$
$wR(F^2) = 0.052$	$(\Delta/\sigma)_{\text{max}} < 0.001$
$S = 1.13$	$\Delta\rho_{\text{max}} = 2.08 \text{ e \AA}^{-3}$
1112 reflections	$\Delta\rho_{\text{min}} = -1.74 \text{ e \AA}^{-3}$
50 parameters	Extinction correction: <i>SHELXL97</i>
	Extinction coefficient: 0.0085 (4)

**Figure 2**

Polyhedral view of $\text{Sm}_2\text{NaIrO}_6$, approximately along [100]. IrO_6 octahedra are shown in red, NaO_6 octahedra in yellow and Sm atoms in black.

Table 1

Selected geometric parameters (\AA , $^\circ$).

$\text{Sm1}-\text{O2}^{\text{i}}$	2.293 (4)	$\text{Na1}-\text{O1}$	2.254 (4)
$\text{Sm1}-\text{O1}^{\text{ii}}$	2.339 (4)	$\text{Na1}-\text{O1}^{\text{vii}}$	2.255 (4)
$\text{Sm1}-\text{O2}$	2.340 (4)	$\text{Na1}-\text{O3}^{\text{iii}}$	2.313 (4)
$\text{Sm1}-\text{O3}^{\text{iii}}$	2.348 (4)	$\text{Na1}-\text{O3}^{\text{iii}}$	2.313 (4)
$\text{Sm1}-\text{O3}^{\text{ii}}$	2.552 (5)	$\text{Ir1}-\text{O2}^{\text{v}}$	1.965 (4)
$\text{Sm1}-\text{O1}$	2.623 (4)	$\text{Ir1}-\text{O2}$	1.965 (4)
$\text{Sm1}-\text{O1}^{\text{iv}}$	2.705 (4)	$\text{Ir1}-\text{O1}$	1.968 (4)
$\text{Sm1}-\text{O3}^{\text{v}}$	2.896 (4)	$\text{Ir1}-\text{O1}^{\text{v}}$	1.968 (4)
$\text{Na1}-\text{O2}^{\text{vi}}$	2.254 (4)	$\text{Ir1}-\text{O3}^{\text{v}}$	1.970 (4)
$\text{Na1}-\text{O2}^{\text{ii}}$	2.254 (4)	$\text{Ir1}-\text{O3}$	1.970 (4)
$\text{Ir1}-\text{O1}-\text{Na1}$	144.0 (2)	$\text{Ir1}-\text{O3}-\text{Na1}^{\text{x}}$	139.2 (2)
$\text{Ir1}-\text{O2}-\text{Na1}^{\text{ix}}$	137.7 (2)		

Symmetry codes: (i) $-x + \frac{3}{2}, y - \frac{1}{2}, -z + \frac{1}{2}$; (ii) $-x + \frac{1}{2}, y - \frac{1}{2}, -z + \frac{1}{2}$; (iii) $x, y - 1, z$; (iv) $x + \frac{1}{2}, -y + \frac{1}{2}, z + \frac{1}{2}$; (v) $-x + 1, -y + 1, -z$; (vi) $x - \frac{1}{2}, -y + \frac{1}{2}, z - \frac{1}{2}$; (vii) $-x, -y, -z$; (viii) $-x, -y + 1, -z$; (ix) $-x + \frac{1}{2}, y + \frac{1}{2}, -z + \frac{1}{2}$; (x) $x, y + 1, z$.

The highest residual electron density and the deepest hole are located approximately 1 \AA from Sm1.

Data collection: *SMART NT* (Bruker, 2001); cell refinement: *SAINT-Plus NT* (Bruker, 2001); data reduction: *SAINT-Plus NT*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 1997); program(s) used to refine structure: *SHELXL97* (Sheldrick, 1997); molecular graphics: *SHELXTL* (Bruker, 2000); software used to prepare material for publication: *SHELXTL*.

This work was supported by the Department of Energy through grant DE-FG02-04ER46122 and the National Science Foundation through grant DMR:0134156. IVP acknowledges the 2004 NSF Summer Research Program in Solid State Chemistry (DMR:0303450) for financial support.

References

Bruker (2000). *SHELXTL*. Version 6.1. Bruker AXS Inc., Madison, Wisconsin, USA.

- Bruker (2001). *SMART NT* (Version 5.625), *SAINT-Plus NT* (Version 6.22) and *SADABS* (Version 6.22). Bruker AXS Inc., Madison, Wisconsin, USA.
- Davis, M. J., Mugavero, S. J. III, Glab, K. I., Smith, M. D. & zur Loye, H.-C. (2004). *Solid State Sci.* **6**, 413–417.
- Gemmill, W. R., Smith, M. D. & zur Loye, H.-C. (2004). *J. Solid State Chem.* **177**, 3560–3567.
- Glazer, A. M. (1972). *Acta Cryst.* **B28**, 3384–3392.
- Mitchell, R. H. (2002). *Perovskites: Modern and Ancient*. Ontario: Almaz Press.
- Mugavero, S. J. III, Smith, M. D. & zur Loye, H.-C. (2005). *J. Solid State Chem.* In the press.
- Sheldrick, G. M. (1997). *SHELXS97* and *SHELXL97*. University of Göttingen, Germany.
- Woodward, P. M. (1997*a*). *Acta Cryst.* **B53**, 32–43.
- Woodward, P. M. (1997*b*). *Acta Cryst.* **B53**, 44–66.